

Environment-friendly sustainable concrete produced from marble waste powder

A. Alex Rajesh^{1*}, P. Prasanthni¹, S. Senthilkumar², B. Priya³

¹Assistant Professor, Department of Civil Engineering, K.S.R College of Engineering, Tiruchengode, Tamil Nadu, India

²Professor, Department of Civil Engineering, K.S.R College of Engineering, Tiruchengode, Tamil Nadu, India


³Associate Professor, Civil Engineering, Nandha Engineering College, Erode, Tamil Nadu, India

Received: 23/06/2023, Accepted: 10/05/2024, Available online: 16/05/2024

*to whom all correspondence should be addressed: e-mail: prasanthni@ksrce.ac.in, alexjack112@gmail.com

<https://doi.org/10.30955/gnj.005204>

Graphical abstract

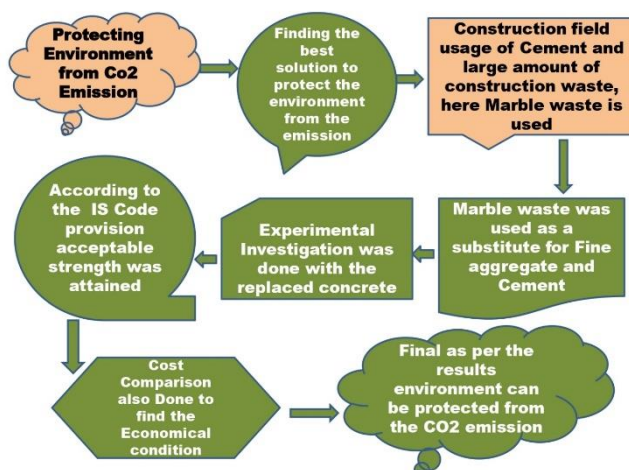

Abstract

Concrete is an indispensable construction material renowned for its versatility and durability, yet its traditional components pose significant environmental challenges. The cement industry is a major emitter of CO₂, while the extensive extraction of natural aggregates depletes finite resources. In response, researchers have explored alternative materials like Marble Waste Powder (MWP) as sustainable substitutes in concrete production. This study investigates the feasibility of incorporating MWP as partial replacements for cement and fine aggregate, examining substitution fractions of 25% and 35%. Through experimental analysis, the mechanical properties and cost implications of these modified concrete blends are evaluated. The research findings reveal that integrating MWP into concrete formulations enables the production of high-strength concrete at a reduced cost, offering a promising solution to enhance the sustainability of construction practices. By partially replacing conventional materials with MWP, the environmental impact associated with concrete production can be mitigated, contributing to efforts aimed at reducing carbon emissions and conserving natural resources. Additionally, the study underscores the

importance of eco-friendly innovations in construction materials, emphasizing the need for sustainable alternatives to meet the growing demand for infrastructure development while minimizing environmental harm. Overall, this research highlights the novel use of MWP as a sustainable alternative in concrete production, showcasing its potential to address environmental concerns and promote more eco-conscious construction practices. Through the exploration of mechanical performance and economic feasibility, the study provides valuable insights for advancing sustainability in the construction industry and achieving long-term environmental stewardship.

Keywords: Marble waste powder (MWP), cement, cost, compressive strength, tensile strength, flexural strength

1. Introduction

Worldwide, many million tonnes of MWP are expected to be created during quarrying. Thus, the practice of marble residue has become a significant alternative material for enhancing the hardening characteristics of concrete (Gholhaki *et al.* 2018). Marble is a sedimentary rock that results from the transformation of pure limestone by metamorphosis. The purity of the marble determines its colour and look; if the limestone is entirely made of calcite, it is white (100 percent CaCO₃). Marble is used in building and decorating because it is sturdy and has a noble appearance. As a result, marble is in high demand (Siddique *et al.* 2021). MWP is produced in huge quantities during the cutting process (Chuc *et al.* 2018). As a result, the amount of marble trash, which accounts for 20% of total marble mined, has risen to millions of tonnes (Singh *et al.* 2017). Directly dumping these waste products into the environment might result in environmental problems (Vardhan *et al.* 2019). Additionally, because natural aggregate and minerals used to make cement are limited, and it is necessary to reduce energy consumption and carbon dioxide emissions associated with construction processes, a solution to this problem is sought through the practice of MWP as a fractional auxiliary for Portland slag cement (Singhal 2018). In India,

MWP is settled by sedimentation and subsequently disposed of, resulting in environmental degradation, as well as the formation of dust during the summer, posing a hazard to agriculture and public health (Ince *et al.* 2020). Thus, the use of the MWP in a variety of industrial sectors, including building, agriculture, glass, and paper, would contribute to environmental protection. Waste may be recycled to create novel goods or utilized as an intermixture to increase the efficiency of natural resource usage and protect the environment from waste deposits (Meng *et al.* 2018)

Alyaseen *et al.* (2023) investigate the impact of design parameters on compressive strength (CS) of high-performance self-compacting concrete (HP-SCC) with recycled concrete aggregate (RCA). Pearson's correlation coefficient analysis and machine learning models (M5P, RF, SVM, LR, ANNs) were employed, with the SVM-PUK-based model showing the highest accuracy, particularly influenced by w/c, w/b, and w/s variables. Alyaseen *et al.* (2023) explore computational techniques like M5P, RF, SVM, and LR to predict concrete splitting strength, addressing its key disadvantage of lower Splitting Tensile Strength (STS). SVM-PUK emerged as the most effective method, emphasizing the significance of curing time (T) among input variables in predicting concrete strength. Alyaseen *et al.* (2023) investigate the impact of *Bacillus Subtilis* bacteria on the strength properties of 100% recycled concrete aggregate (RCA) with silica fume (SF) substitution for cement. Optimal results were observed with 7.5% SF substitution. SEM and EDS analysis confirmed calcite precipitation, densifying the concrete and improving compressive and splitting tensile strength. Sharma *et al.* (2022) evaluates concrete flexural strength using waste marble powder and machine learning methods like ANFIS, SVM, and Gaussian processes. With a dataset of 202 observations split into training and testing sets, Gaussian processes outperformed others with a higher correlation coefficient and lower error values, identifying curing days as a significant predictor. Upadhy *et al.* (2023) study aims to determine the optimal prediction model for Marshall Stability and Bitumen Content (BC) in carbon fiber reinforced asphalt concrete. Employing machine learning techniques and statistical metrics, Random Forest emerged as the best model, with BC of approximately 5.0% identified as a significant factor influencing Marshall Stability. Sharma *et al.* (2022) research aims to predict concrete compressive and flexural strengths using waste marble powder as partial replacements. Support Vector Machines, Gaussian Processes, and other models were applied to experimental data. Gaussian Process and Support Vector Machines Stochastic showed superior performance, offering higher correlations and lower errors, suggesting their suitability for strength prediction. Sharma *et al.* (2023) study assesses the impact of waste marble powder on concrete flexural strength using machine learning algorithms. Five models were evaluated, with Gaussian Process performing best, showing a CC of 0.8108 and lower RMSE (2.6025 MPa) and RRSE (59.32%). Sensitivity analysis identified specific concrete mixes as sequentially

sensitive due to lower CC values (Mohanraj and Vidhya, 2024). Due to the lower quality criteria for resources, concrete blocks appear to be the most preferred alternative for using recovered waste materials (Shukla *et al.* 2020). This article covers published studies on the use of several types of waste in the manufacturing of concrete blocks, including recycled concrete, crushed brick, soda lime glass, cathode ray tube glass, crumb rubber, and ceramic and tile waste (Chima *et al.* 2022). The amount of these elements integrated into concrete blocks can be increased to 100% as a substitute for natural aggregate, or it can be reduced to less than 30% in specific applications to fulfill the standard requirement (Dilbas *et al.* 2019; Sathyakumar and Divya 2019; Mohanraj *et al.* 2023). Researchers identified the most important physicochemical characteristics of conventional cement and marble powder (Yaragal *et al.* 2019). Marble mud powder can be used to aid in filling voids in concrete construction (Khodabakhshian *et al.* 2018). This article demonstrates how to utilise marble mud dust as a 100 percent substitute for real sand in concrete (Tejaswini and Rao 2020). The compression strength and microstructure of mixed cement were investigated in this study (Lam *et al.* 2017). The stronger the marble, the more dust it holds (Mohanraj *et al.* 2022). Sharma *et al.* employs waste marble powder to predict concrete strength (Prasanthni *et al.* 2024). Gaussian process and SVM techniques exhibit superior performance with high correlation coefficients, lower error values, and reduced experimental time, suggesting their reliability in predicting compressive and flexural strength. Sharma *et al.* assesses concrete flexural strength using machine learning methods like ANFIS, SVM, and Gaussian processes (Prasanthni and Palanisamy, 2016). Sensitivity analysis identifies influential factors. Gaussian process shows superior performance, with high correlation coefficient (0.7476), lower mean absolute error (1.0884), and root mean square error (1.5621). Curing days are found significant. Alyaseen *et al.* explores the impact of *Bacillus Subtilis* bacteria on the strength properties of 100% recycled concrete aggregate incorporating silica fume (Krishnasamy *et al.* 2023). Results indicate enhanced compressive and splitting tensile strengths due to calcite precipitation, leading to denser concrete. Economic analysis and regression equations validate the findings, meeting Indian concrete specifications. Upadhy *et al.* identified the optimal prediction model for Marshall Stability and Bitumen Content in carbon fiber reinforced asphalt concrete for flexible pavements (Johnson *et al.* 2024). Five machine learning techniques were applied, with Random Forest showing the best performance. Sensitivity analysis revealed a significant influence of 5.0% binder content on Marshall Stability. The objective of this research is to investigate the feasibility of using marble debris as a partial substitute for concrete production (Hansen *et al.* 2018). Specifically, the study aims to determine the mechanical characteristics and cost implications of incorporating marble debris at two different replacement percentages: 25% and 35%. By doing so, the research seeks to identify the optimal replacement ratio that

maximizes concrete performance while minimizing costs. One novelty of this research lies in its focus on exploring marble debris as an alternative material for concrete production. While previous studies [1-52] have examined various supplementary materials for concrete, the use of marble debris in this context is relatively underexplored. Additionally, the research investigates two different replacement percentages, providing insights into the effect of varying substitution levels on concrete properties and cost (Madenci *et al.* 2019). The existing literature lacks comprehensive studies on the utilization of marble debris as a partial substitute for concrete, particularly with regards to its mechanical characteristics and cost implications (El-Shafie 2020). While some studies have explored the use of alternative materials in concrete production, there is a gap in knowledge regarding the specific effects of marble debris substitution on concrete properties and cost-efficiency (Li *et al.* 2019). Therefore, this research aims to fill this gap by providing a detailed analysis of the mechanical characteristics and cost considerations associated with incorporating marble debris in concrete mixes at different replacement percentages.

This study addresses the scarcity of research comparing the impact of marble waste powder (MWP) substitution for fine aggregate versus cement in M40 grade concrete. It aims to assess mechanical properties such as flexural-

Table 1. Characteristics of replacing materials in concrete mix

+Characteristics	Normal Weight Coarse Aggregate (NWA) (5mm-20mm)	Normal Fine Aggregate (NFA) (less than 4.75mm)	MWP
Specific gravity	2.8	2.7	2.7
Fineness	6.7	2.5	3
Abrasion %	42	-	-
Moisture Content %	0.9	1.3	0.12
Water absorption %	0.6	0.98	4.9
Bulk density (t/m ³)	1.9	1.6	1.4

Table 2. Description concrete mix proportions

Mix ID	f_{cu} (MPa)	f_c (MPa)	f_{ct} (MPa)	E (GPa)
A0	53	46	41	4.3
Acc25	56	52	57	3.6
Acc35	61	51	54	3.5
Acfa25	65	59	51	3.8
Acfa35	63	54	59	3.7



Figure 1. Materials used in current study A) NFA B) Cement C) 20mm NWA D)10mm NWA E) MWP F) MFA

tensile strength (FTS) and elasticity, often overlooked in previous studies focused solely on compressive strength. Moreover, the research provides a vital cost estimate for market viability, enhancing understanding of MWP utilization in concrete. By emphasizing these aspects, the study seeks to contribute valuable insights into optimizing MWP incorporation in concrete mixtures, thereby advancing sustainable construction practices and resource management in the industry.

2. Materials and methodology

The goal of this study was to conduct an experiment to see if 25% and 35% MWP could be applied as a partial supplement for PC and fine aggregate in construction mixes (Varshney; Li *et al.* 2020; Velumani *et al.* 2023). Because the existing literature has indicated that these percentages may be used without substantial reduction, the high percentages of 25% and 35% were chosen (Krishnasamy *et al.* 2024; Johnson *et al.* 2010; Padmapoorani *et al.* 2023; Pattusamy *et al.* 2023; Ravikumar *et al.* 2023). In order to assess the economic viability of this substitution, the physical behaviour of the new concrete was compared to the cost (Loganathan *et al.* 2022) As shown in Figure 1, all of the ingredients utilised in the mixes are as follows:

The Portland Cement that was utilised in this experiment was manufactured by UltraTech Cement in India (Palanisamy and Kumarasamy 2023). In this experimental investigation, mixtures of 10 and 20mm Normal Weight Aggregates (NWA's) are employed (Rajesh *et al.* 2023). ASTM C33 standards were used to conduct several tests (Table 1 summarises the results of these testing) (Velumani *et al.* 2023). Additionally, the ratio of coarse aggregates (1 -20 cm) employed to present investigation is one part to 4 parts (Prasanthni *et al.* 2023). In this research, river sand fine aggregate is utilised to create the mixtures. ASTM-compliant tests (Table 1) were revealed (Krishnaraja and Kandasamy 2018). The marble scraps utilised in this project are from Indian industrial trash. This waste was collected and crushed into particles (size ~4

mm) for use in substitution of fine aggregate (Johnson and Thirugnanam 2015). Marbles are crystalline rocks that are mostly made of calcite, dolomite, or serpentine minerals. The remaining mineral components differ according to their origin. Magnesia, phosphate, lead, zinc, alkalis, and sulphides are the major contaminants in fresh CaO (to cement) that might alter the characteristics of final cement. The characteristics of Marble Fine Aggregate are illustrated in Table 1. The specific gravity of MFA is lesser than Normal Fine Aggregate (NFA). Additionally, it is more refined because to the significantly lower fineness modulus (3.0). In comparison to the NFA, the MFA has a significantly higher water absorption capacity and a higher moisture content. Apart from MFA, Marble Waste Powder (MWP) from the marble polishing process was utilised in place of cement in some instances (Gurunaathan *et al.* 2017). The naphthalene sulphonated superplasticizer (NSSP) was added to make concrete more workable

Table 3. Test abstract concrete mix (56 days)

ID	Materials (kg/m ³)							
	Cement	MWP	NWA		NFA	MFA	Water	NSSP
			20 mm	10 mm				
A0	420		720	270	820		183	5.25
Acc25	315	75	720	270	820		183	5.25
Acc35	273	147	720	270	820		183	5.25
Acfa25	420		720	270	615	205	183	5.25
Acfa35	420		720	270	533	287	183	5.25

Table 4. Chemical composition of cement and marble powder

Elements	Cement	Marble Powder
Calcium oxide	66	56
Silica oxide	30	1
Aluminium oxide	5	0.5
Iron oxide	3	0.3
Magnesium oxide	2	0.2
Potassium oxide	0.48	-
Sulphur trioxide	0.5	-
Calcium carbonate	-	0.9
Chloride	0.1	0.1
LOI	1	42.9
Specific density	3	2.69
Blaine Surface (cm ² /g)	2792	2126

2.1. Mix proportioning and specimen preparation

The concrete mix design was performed in accordance with ASTM standards in order to meet the A40 concrete grade requirement (Loganathan *et al.* 2022). The objective of the grade A40 is to reach a typical f_{cc} (Cylindrical compression strength \sim forty MPa) and f_c (mean Cylindrical compression strength \sim fifty MPa). Table 2 shows the mix proportions.

2.2. Test methods

Water-cured specimens corresponding to each concrete mix outlined in Table 2 were fabricated and kept in storage until the testing phase. As depicted in Figure 2, the specimens include cubes with dimensions of 15 x 15 x 15 cm, cylinders with a diameter of 15 cm, and a height of 30 cm. These specimens were utilized to determine the compressive strength and elasticity. Moreover, beam

(Krishnaraja *et al.* 2019). For all mixes, the content of NSSP was 1.25 % of the weight of cement.

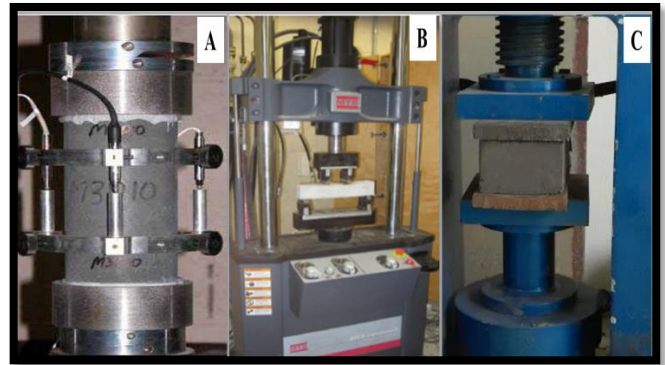


Figure 2. Machines used for test study A) Elasticity B) Flexural-tensile strength C) Compressive strength

samples measuring 10 x 10 cm in cross-section and 50 cm in length were prepared for a four-point flexural tensile test (Rajesh *et al.* 2023). The tests were conducted on the 56th day to ensure minimal strength reduction due to hydration. Figure 2 provides an illustration of the testing apparatus utilized in the experiments.

3. Results

The findings of the experiments that were carried out on concrete cubes on day 56 are summarised in Table 3, where f_{cu} (Cube compression strength), f_c (Cylindrical compression strength), E (elasticity) and f_{ct} (flexural-tensile strength) respectively.

4. Discussion

The MWP is a significant waste product generated in the stone industry during the cutting, shaping, and polishing

of marbles. Around 20%–25% of the marble used in this procedure is converted to powder. India is the globally third largest exporter of marble (~10%), and each year, millions of tonnes of marble debris from processing facilities are dumped. This project was planned and preceded due to the availability of a huge quantity of trash generated by the marble industry. The chemical characteristics of MWP are summarised in Table 4. To

determine the findings, the MWP content of Calcium Oxide (CaO) was 55.6 percent for the marble, which is in compliance with the criteria for natural cement, which is 65.9 percent. However, additional components like as SiO₂, Al₂O₃, Fe₂O₃, and MgO do not fit within the parameters of ordinary natural cement. This means that MWP is classified as natural cement but does not operate entirely like natural cement (Table 5).

Table 5. Cost of each concrete mix as per Indian standards

Material	Cement/Kg	MWP/Kg	NWA/Kg (20mm)	NWA/Kg (10mm)	NFA/Kg	NSSP/Kg
Cost in Rs.	6.8	0.88	0.440	0.655	0.94	40

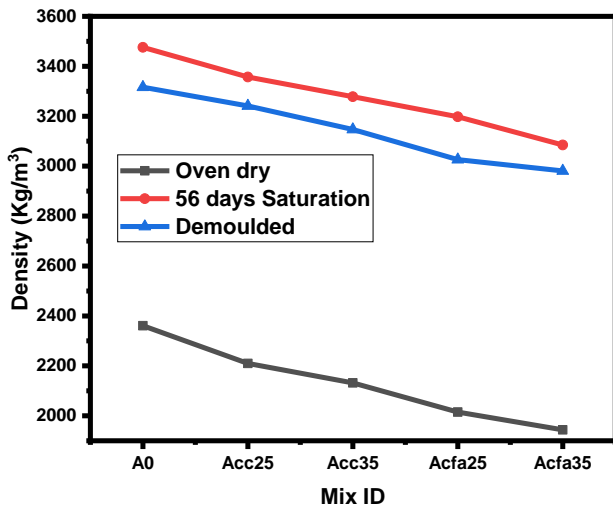


Figure 3. Density of each mix

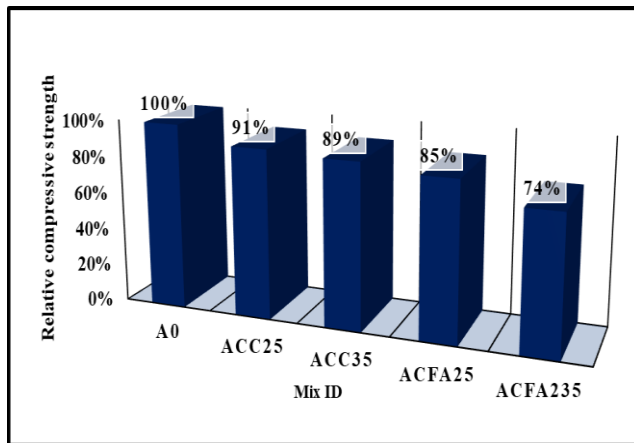


Figure 4. Relative compressive strength percentages between each mix with control

4.1. Density

Figure 3 depicts the relationship between each concrete mix and its corresponding densities. The findings revealed a decrease in the densities of all three types of concrete, attributed to the lower specific gravity of Marble Waste Powder (MWP) and Marble Fine Aggregate (MFA) compared to Natural Washed Aggregate (NWA). When considering only the oven dry density (ODD) of concrete, it ranged from 2361 kg/m³ to 1944 kg/m³. Furthermore, the density of demoulded concrete varied between 3316 kg/m³ and 2981 kg/m³. This alteration in density affects the strength characteristics of the concrete (Alyaseen *et al.* 2023).

4.2. Compressive strength

The Cylindrical compression strength (f_c) values in Table 4 may be examined in detail by referring to Figure. 4, which depicts the comparative ratios of the standard mix and the other mixes. According to Figure 4, a compressive strength decreases of between 9 and 26% was found. The compressive strength is lowest when 35% of the cement is substituted by marble (Acc35), while the compressive strength is greatest when 25% of the cement is replaced by marble (Acc25). Additionally, it can be demonstrated that using more MFA rather than NFA results in increased strength (Acfa35). Table 4 cylindrical compression strength may be described using Figure 4 displays the relative ratios(percentages) of the standard mix (MO) vs the individual mixes. According to Figure.4. A decrease in compressive strength was reported in a range of 9-26 percent. The lowest compressive strength was recorded when marble replaced 35 percent of the cement (Acc35), while the highest compressive strength was recorded when marble replaced 25 percent of the cement (Acc25) (Alyaseen *et al.* 2023). Furthermore, it has been demonstrated that using more MFA rather than NFA results in greater strength (Acfa35).

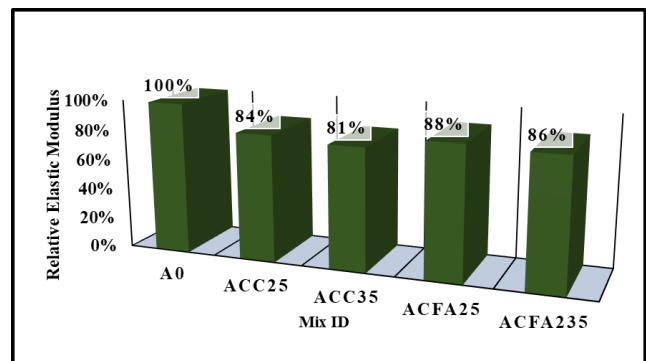


Figure 5. Relative elasticity percentages between each mix with control

4.3. Elasticity

Figure 5 depicts a comparison of the elasticity of the material mixes in concrete (Table 3) in terms of comparative percentages, where A₀ represents the standard mix and is assumed to be 100%. As was the case with compressive strength, Acc25 recorded the lowest elasticity once again. 25% cement substitution results in a 3% increase in elasticity over Acc35. A low elasticity might cause structural components to deflect more. It is worth noting, that a lower cement concentration lowers

concrete's long-term impacts, such as shrinkage and creep. This contributes to the reduction of bend and moderates the result of the reported decrease in the E (elasticity). Figure. 4 indicates that substituting 25% NFA for MFA (Acfa25) reduces the elasticity by just 12% compared to the standard mix [Alyaseen *et al.* 2023]. Increased NFA replacement results in a decrease in elasticity (Acfa35).

4.4. Flexural Strength

The relative differences between the control mix and other concrete mixes were analyzed based on the flexural test results presented in Table 3 and illustrated in Figure 6. The investigation revealed a discernible impact of cement substitution on the tensile strength of the concrete specimens. Specifically, there was a notable decrease in tensile strength, with a 10% reduction observed when 25% of the cement was replaced (Acc25), and a more significant 17% reduction observed with a 35% cement replacement (Acc35). Notably, the smallest decline of 24% was observed when 25% of the Natural Fine Aggregate (NFA) was substituted with Marble Fine Aggregate (MFA) (Acfa25) (Sharma *et al.* 2022). However, as the substitution of NFA was increased further, the decline in tensile strength became more pronounced, particularly evident in the case of Acfa35. These findings underscore the influence of cement and aggregate substitutions on the mechanical properties of the concrete, highlighting the importance of optimizing mix proportions to achieve desired strength characteristics while incorporating alternative materials.

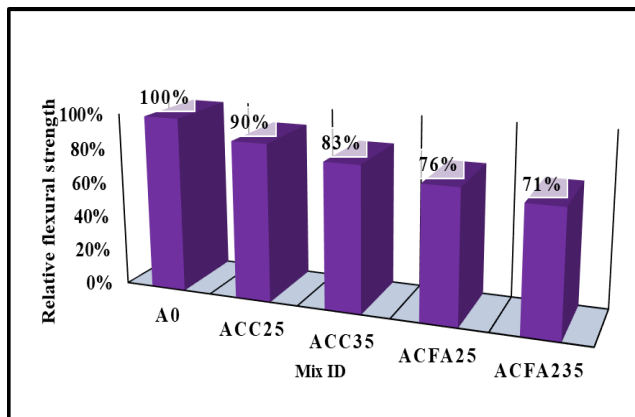


Figure 6. Relative elasticity percentages between each mix with control

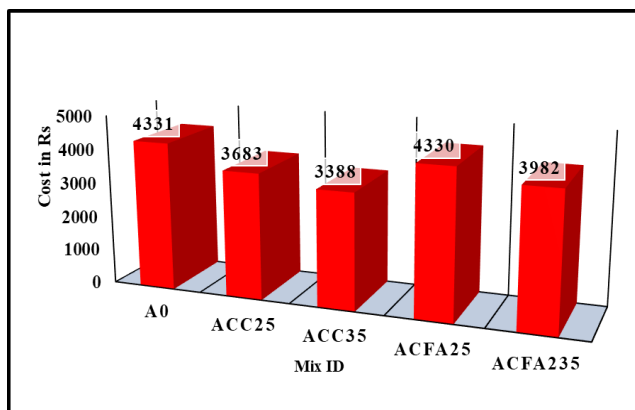


Figure 7. Cost of Mix

4.5. Cost

A comprehensive cost analysis was conducted to evaluate the economic feasibility of producing different material combinations presented in Table 2. Market prices of individual constituents used in concrete production were determined based on prevailing rates in India in 2021, as outlined in Table 5. The total cost of each combination was examined, revealing a significant impact of cement substitution on reducing overall costs. Notably, the price of Acc25 decreases by 15% with a 25% cement replacement, while Acc35 experiences a more substantial 22% decrease with a 35% cement replacement. Conversely, substituting Natural Fine Aggregate (NFA) with Acfa25 and Acfa35 yields no significant cost reduction. Marble Waste Powder (MWP) emerges as the most economically viable substitute for cement. However, substituting MWP for Fine Aggregate (F.A) does not yield economic benefits. To assess the cost-effectiveness of each combination, the compressive strength of each blend was compared to its cost, with compressive strength chosen as it best reflects concrete material properties. For instance, steel reinforcement can enhance concrete's tensile strength. In Figure 8, the cylindrical compression strength is juxtaposed with the cost of each combination. Notably, Acc25 emerges as a blend with both high compressive strength and low cost, demonstrating that replacing 25% of cement with MWP results in superior compressive strength at a lower cost.

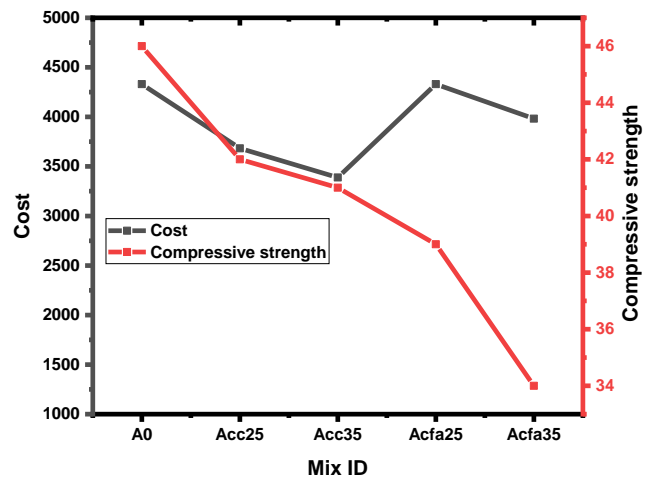


Figure 8. Comparison of cost with compressive strength of each Mix

5. Conclusion

This study aimed to investigate the viability of utilizing marble debris as a substitute material in concrete production, focusing on two replacement percentages: 25% and 35%. Mechanical properties and cost analyses were conducted for each combination to assess their suitability for practical application. It was observed that a maximum cement replacement of 25% yielded satisfactory mechanical characteristics, beyond which further substitution led to diminished mechanical performance. Additionally, the replacement of natural fine aggregate had negligible effects on pricing. However, increased substitution of marble debris adversely impacted elasticity and tensile strength. Notably, a

minimal increase in compressive strength was observed with 35% marble fine aggregate (MFA) substitution. Cost analysis revealed that substituting cement resulted in a reduction in material costs. Overall, the findings suggest that a 25% replacement of cement with marble debris is the optimal choice for achieving a high-quality concrete mix at a reasonable cost. This study underscores the importance of balancing material substitution with mechanical requirements and cost considerations in concrete production, providing valuable insights for sustainable construction practices.

Acknowledgement

The authors are expressing their sincere gratitude to KSR College of engineering for providing infrastructural facilities to complete this research.

References

- Alyaseen A., Poddar A., Kumar N., Haydar K., Khan A., Sihag P. and Singh T. (2023). Influence of silica fume and *Bacillus subtilis* combination on concrete made with recycled concrete aggregate: Experimental investigation, economic analysis, and machine learning modeling. *Case Studies in Construction Materials*, **19**, e02638. <https://doi.org/10.1016/j.cscm.2023.e02638>
- Alyaseen A., Poddar A., Kumar N., Tajjour S., Prasad C.V.S.R., Alahmad H. and Sihag P. (2023). High-performance self-compacting concrete with recycled coarse aggregate: soft-computing analysis of compressive strength. *Journal of Building Engineering*, **77**, 107527. <https://doi.org/10.1016/j.jobe.2023.107527>
- Alyaseen A., Siva Rama Prasad C.V., Poddar A., Kumar N., Mostafa R.R., Almohammed F. and Sihag P. (2023). Application of soft computing techniques for the prediction of splitting tensile strength in bacterial concrete. *Journal of Structural Integrity and Maintenance*, **8**(1), 26–35. <https://doi.org/10.1080/24705314.2022.2142900>
- Chima O.M. Analysis of the biomechanical properties of portland cement based on the particle size distribution and chemical oxide composition.
- Chuc N.T., Van L.T. and Bulgakov B.I. (2018). Designing the composition of concrete with mineral additives and assessment of the possibility of cracking in cement-concrete pavement, in *Materials Science Forum*, **931**, 667–673.
- Dilbas H., Çakır Ö. and Atiş C.D. (2019). Experimental investigation on properties of recycled aggregate concrete with optimized Ball Milling Method, *Construction and Building Materials*, **212**, 716–726.
- El-Shafie Y.M. (2020). Waste from stone industry as a cement additive towards a reduced carbon footprint of concrete, PhD Thesis, University of Stuttgart.
- Gholhaki M., Hajforoush M. and Kazemi M. (2018). An investigation on the fresh and hardened properties of self-compacting concrete incorporating magnetic water with various pozzolanic materials, *Construction and Building Materials*, **158**, 173–180.
- Gurunaathan K., Johnson S.C. and Thirugnanam G.S. (2017). Anticipated and actual performance of composite girder with pre-stressed concrete beam and RCC top flange. *Structural Engineering and Mechanics International Journal*, **61**(1), 117–124.
- Hansen S.G., Lauridsen J.T. and Hoang L.C. (2018). Experimental and statistical investigation of the compressive strength anisotropy in structural concrete, *Cement and Concrete Research*, **107**, 304–316.
- Ince C., Hamza A., Derogar S. and Ball R.J. (2020). Utilisation of waste marble dust for improved durability and cost efficiency of pozzolanic concrete, *Journal of Cleaner Production*, **270**, 122213.
- Johnson B.G.C., Ramasamy M. and Narayanan A. (2024). Experimental study and assessment of the structural performance of laced reinforced concrete beams against reverse cyclic loading. *Matéria (Rio de Janeiro)*, **29**(1), e20240001. <https://doi.org/10.1590/1517-7076-RMAT-2024-0001>
- Johnson S.C. and Thirugnanam G.S. (2010). Experimental study on corrosion of transmission line tower foundation and its rehabilitation. *International Journal of Civil & Structural Engineering*, **1**(1), 27–34.
- Johnson S.C. and Thirugnanam G.S. (2015). Structural integrity assessment of transmission line tower foundations: a comprehensive approach. *CIGRE India Journal*, **4**(2), 42–49.
- Khodabakhshian A., De Brito J., Ghalehnovi M. and Shamsabadi E.A. (2018). Mechanical, environmental and economic performance of structural concrete containing silica fume and marble industry waste powder, *Construction and Building Materials*, **169**, 237–251.
- Krishnaraja A.R. and Kandasamy S. (2018). Flexural performance of hybrid engineered cementitious composite layered reinforced concrete beams. *Periodica Polytechnica Civil Engineering*, **62**(4), 921–929. doi: <http://dx.doi.org/10.3311/PPci.11748>.
- Krishnaraja A.R., Anandakumar S., Jegan M. et al. (2019). Study on impact of fiber hybridization in material properties of engineered cementitious composites. *Matéria (Rio de Janeiro)*, **24**(2), e12347. doi: <http://dx.doi.org/10.1590/s1517-707620190002.0662>.
- Krishnasamy R., Johnson S.C., Kumar P.S. and Mohanraj R. (2023). Experimental Investigation of Lateral Load Test on Diagonal Braced 3M Glass Fiber Reinforced Polymer Transmission Tower. *Power Research-A Journal of CPRI*, **19**(2), 225–231. <https://doi.org/10.33686/pwj.v19i2.1150>
- Krishnasamy R., Singaram C.J., Palanichamy S. and Mohanraj R. (2024) Testing and Evaluation of Buckling and Tensile Performance of Glass Fiber-Reinforced Polymer Angle Section with Different Joints/Connections. *Journal of Testing and Evaluation*, **52**(1), 1–16. <http://doi.org/10.1520/JTE20230010>
- Krisnamurti K., Soehardjono A., Zacoeb A. And Wibowo A. Development of Mix Design Method in Efforts to Increase Concrete Performance Using Portland Pozzolana Cement (PPC).
- Lam M.N.-T., Jaritngam S. and Le D.-H. (2017). Roller-compacted concrete pavement made of Electric Arc Furnace slag aggregate: Mix design and mechanical properties, *Construction and Building Materials*, **154**, 482–495.
- Li L.G., Huang Z.H., Tan Y.P., Kwan A.K.H. and Chen H.Y. (2019). Recycling of marble dust as paste replacement for improving strength, microstructure and eco-friendliness of mortar, *Journal of Cleaner Production*, **210**, 55–65.
- Li Z., Lu D. and Gao X. (2020). Optimization of mixture proportions by statistical experimental design using

- response surface method-A review, *Journal of Building Engineering*, 102101.
- Loganathan P., Mohanraj R., Senthilkumar S. and Yuvaraj (2022) Mechanical performance of ETC RC beam with U-framed AFRP laminates under a static load condition. *Revista de la Construcción.*, **21**(3), 678–691. <https://doi.org/10.7764/RDLC.21.3.678>
- Madenci E., Özkılıç Y.O. and Gemi L. (2019). The Effects of Length to Depth Ratio on the Reinforced Concrete Pultruded GFRP Beams, in 1st International Symposium on Innovations in *Civil Engineering and Technology*, 386–391.
- Meng Y., Ling T.-C. and Mo K.H. (2018). Recycling of wastes for value-added applications in concrete blocks: An overview, *Resources, Conservation and Recycling*, **138**, 298–312
- Mohanraj R. and Vidhya K. (2024). Evaluation of compressive strength of Euphorbia tortilis cactus infused M25 concrete by using ABAQUS under static load. *Materials Letters.*, **356**, 135600. <https://doi.org/10.1016/j.matlet.2023.135600>
- Mohanraj R., Senthilkumar S. and Padmapoorani P. (2022). Mechanical properties of RC beams With AFRP sheets under a sustained load. *Materials and Technology.*, **56**(4), 365–372. <https://doi.org/10.17222/mit.2022.481>
- Mohanraj R., Senthilkumar S., Goel P. and Bharti R. (2023). A state-of-the-art review of Euphorbia Tortilis cactus as a bio-additive for sustainable construction materials. *Materials Today: Proceedings*. <https://doi.org/10.1016/j.matpr.2023.03.762>
- Mohanraj R., Senthilkumar S., Shanmugasundaram S. and Padmapoorani P. (2022). Torsional performance of reinforced concrete beam with carbon fiber and aramid fiber laminates. *Revista de la Construcción.*, **21**(2), 329–337. <https://doi.org/10.7764/RDLC.21.2.329>
- Padmapoorani P., Senthilkumar S. and Mohanraj R. (2023). Machine Learning Techniques for Structural Health Monitoring of Concrete Structures: A Systematic Review. *Iranian Journal of Science and Technology, Transactions of Civil Engineering*, **47**(4). <https://doi.org/10.1007/s40996-023-01054-5>
- Palanisamy G. and Kumarasamy V. (2023). Rehabilitation of damaged RC exterior beam-column joint using various configurations of CFRP laminates subjected to cyclic excitations. *Matéria (Rio de Janeiro).*, **28**(2), e20230110. doi: <http://dx.doi.org/10.1590/1517-7076-rmat-2023-0110>.
- Pattusamy L., Rajendran M., Shanmugamoorthy S., Ravikumar K. (2023). Confinement effectiveness of 2900psi concrete using the extract of Euphorbia tortilis cactus as a natural additive. *Matéria (Rio de Janeiro).*, **28**(1). <https://doi.org/10.1590/1517-7076-RMAT-2022-0233>
- Prasanthni P. and Palanisamy T. (2016) Mechanical Characteristics and Structural Behaviour of Engineered Cementitious Composites using Polyvinyl Alcohol Fiber. *Asian Journal of Research in Social Sciences and Humanities*, **6**(7), 749-761. DOI: 10.5958/2249-7315.2016.00460.3
- Prasanthni P., Priya B., Dineshkumar G. and gobinath G.N. (2023). Mechanical properties of coal ash concrete in the presence of graphene oxide. *International Journal of Coal Preparation and Utilization. In press*. doi: <http://dx.doi.org/10.1080/19392699.2023.2284991>
- Prasanthni P., Priya B., Palanisamy T. and Dineshkumar G. (2024). Enhancing PVCC beam performance through PVA fiber and basalt fabric in sustainable construction: ductility, strength, and energy absorption improvements. *Matéria (Rio de Janeiro)*, **29**(1), e20230299. <https://doi.org/10.1590/1517-7076-RMAT-2023-0299>
- Rajesh A.A., Senthilkumar S. and Samson S. (2023). Optimal proportional combinations of rubber crumbs and steel slag for enhanced concrete split tensile strength. *Matéria (Rio de Janeiro).*, **28**(4), e20230206. doi: <http://dx.doi.org/10.1590/1517-7076-rmat-2023-0206>.
- Rajesh A.A., Senthilkumar S. and Sargunan K. (2023). Interpolation and extrapolation of flexural strength of rubber crumbs and coal ash with graphene oxide concrete. *Matéria (Rio de Janeiro).*, **28**(4), e20230179. doi: <http://dx.doi.org/10.1590/1517-7076-rmat-2023-0179>.
- Ravikumar K., Palanichamy S., Singaram C.J., Rajendran M. (2023). Crushing performance of pultruded GFRP angle section with various connections and joints on lattice towers. *Matéria (Rio de Janeiro).*, **28**, e20230003. <https://doi.org/10.1590/1517-7076-RMAT-2023-0003>
- Sathyakumar N. and Divya A. (2019). Experimental investigation on manufactured sand (m-sand) for determining the basic properties and compare the results with river sand in zone-II, in *AIP Conference Proceedings*, **2128**(1), 020008.
- Seghir N.T., Mellas M., Sadowski L. and Žak A. (2018). Effects of marble powder on the properties of the air-cured blended cement paste, *Journal of Cleaner Production*, **183**, 858–868
- Sharma N., Thakur M.S., Kumar R., Malik M.A., Alahmadi A.A., Alwetaishi M. and Alzaed A.N. (2022). Assessing waste marble powder impact on concrete flexural strength using Gaussian process, SVM, and ANFIS. *Processes*, **10**(12), 2745. <https://doi.org/10.3390/pr10122745>
- Sharma N., Thakur M.S., Sihag P., Malik M.A., Kumar R., Abbas M. and Saleel C.A. (2022). Machine learning techniques for evaluating concrete strength with waste marble powder. *Materials*, **15**(17), 5811. <https://doi.org/10.3390/ma15175811>
- Sharma N., Thakur M.S., Upadhy A. and Sihag P. (2023). Assessment of flexural strength of concrete with marble powder applying soft computing techniques. *Journal of Building Pathology and Rehabilitation*, **8**(1), 4. <https://doi.org/10.1007/s41024-022-00251-5>
- Shukla A., Gupta N. and Gupta A. (2020). Development of green concrete using waste marble dust *Materials Today: Proceedings*, **26**, 2590–2594
- Siddique S., Jang J.G. and Gupta T. (2021). Developing marble slurry as supplementary cementitious material through calcination: Strength and microstructure study, *Construction and Building Materials*, **293**, 123474.
- Singh M., Choudhary K., Srivastava A., Sangwan K.S. and Bhunia D. (2017). A study on environmental and economic impacts of using waste marble powder in concrete, *Journal of Building Engineering*, **13**, 87–95,
- Singhal A. (2018). Environmental Impacts of Sandstone Quarrying at Keru, Jodhpur, Rajasthan, *Indian Institute of Technology Kharagpur*.
- Tejaswini G.L.S. and Rao A.V. (2020). A detailed report on various behavioral aspects of self-compacting concrete, *Materials Today: Proceedings*, **33**, 839–844.
- Upadhy A., Thakur M.S., Sihag P., Kumar R., Kumar S., Afeeza A. and Saleel C.A. (2023). Modelling and prediction of binder content using latest intelligent machine learning algorithms in carbon fiber reinforced asphalt concrete. *Alexandria*

Engineering Journal, **65**, 131–149.

<https://doi.org/10.1016/j.aej.2022.09.055>

Vardhan K., Siddique R. and Goyal S. (2019). Influence of marble waste as partial replacement of fine aggregates on strength and drying shrinkage of concrete, *Construction and Building Materials*, **228**, 116730.

Varshney H, An Experimental Study on Reactivity of Silica Fume and Copper Slag in Concrete, *Journal of Construction & Building Materials Engineering*, **3**(1).

Velumani M., Mohanraj R., Krishnasamy R. and Yuvaraj H.Y. (2023). Durability Evaluation of Cactus-Infused M25 Grade Concrete as a Bio-Admixture. *Periodica Polytechnica Civil Engineering.*, **67**(4), 1066–1079.

<https://doi.org/10.3311/PPci.22050>

Yaragal S.C., Gowda S.B. and Rajasekaran C. (2019). Characterization and performance of processed lateritic fine aggregates in cement mortars and concretes, *Construction and Building Materials*, **200**, 10–25, 2019.