

# Natural Pigment Based Dye Sensitized Solar Cells: Photovoltaic Studies: A sustainable energy solution

Kanchan Ranwa<sup>1</sup>, Hukma Ram Khakhal<sup>2</sup>, Deeksha Kharkwal<sup>3</sup>, Shweta Vyas<sup>1\*</sup>, Rabia Ejaz<sup>4</sup>, Islem Abid<sup>5</sup>, Humaira Rizwana<sup>6</sup>, Saltanat Aghayeva<sup>7</sup>, Rashid Iqbal<sup>7,8\*</sup>

<sup>1</sup> Department of Pure and Applied Chemistry, University of Kota, Kota 324005, Rajasthan, India

<sup>2</sup> Department of Pure and Applied Physics, University of Kota, Kota 324005, Rajasthan, India

<sup>3</sup> School of Basic and applied Sciences, Anand International College of Engineering Jaipur, 303012, Rajasthan, India

<sup>4</sup> Frontiers Science Center for Rare Isotopes & School of Nuclear Science and Technology, Lanzhou University, Lanzhou 730000, China

<sup>5</sup> Centre of Excellence in Biotechnology Research, King Saud University, P.O Box 2455, Riyadh 11495, Saudi Arabia


<sup>6</sup> Department of Botany and Microbiology, College of Science, King Saud University, Riyadh 11451, Saudi Arabia

<sup>7</sup> Department of Life Sciences, Western Caspian University, Baku, Azerbaijan

<sup>8</sup> Department of Agronomy, Faculty of Agriculture and Environment, The Islamia University of Bahawalpur, Bahawalpur 63100, Pakistan

\*Correspondence: [shwetavyas@uok.ac.in](mailto:shwetavyas@uok.ac.in); [rashid.iqbal@iub.edu.pk](mailto:rashid.iqbal@iub.edu.pk)

## Graphical Abstract

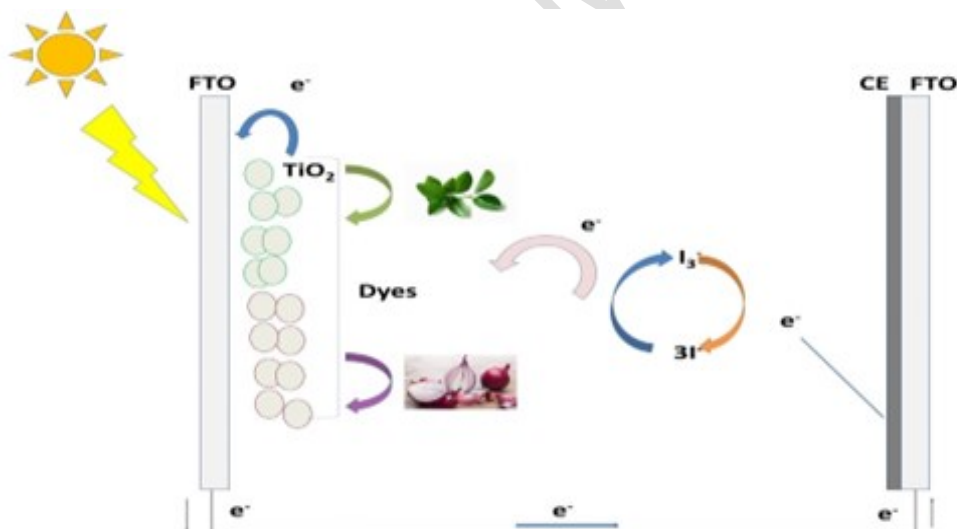

## Abstract

The present research work is carried out on fabrication of natural pigment-based dye-sensitized solar cells (DSSCs) utilizing Lemon leaves and Onion peels extracted dyes as natural photosensitizers. The absorption spectra analysis shows the major peaks for onion peel at 370 nm and 475 nm and 664 nm for lemon leaf that provides valuable insights regarding the

29 narrowing of band gap of TiO<sub>2</sub> from standard value (3.25eV) to 2.87 and 2.44 eV by  
30 incorporation of Onion peel and Lemon leaf pigments respectively and showing the potential  
31 of natural pigments for renewable energy applications. The photovoltaic parameters revealed  
32 that the Lemon leaf extract exhibited higher power conversion efficiency (0.92%) than the  
33 Onion peel extract with an efficiency of 0.054%. Additionally, impedance analysis was  
34 conducted to understand the charge transport and recombination processes within the DSSCs  
35 which revealed a better lifetime of 0.0349 sec for lemon leaf and 0.0143 sec for onion peel  
36 extracted DSSCs. The preliminary photovoltaic results indicated the potential of Lemon leaf  
37 and Onion peel extracts as eco-friendly and cost-effective natural photosensitizers for DSSCs  
38 using Platinum free counter electrode.

39 **Keywords:** TiO<sub>2</sub>, DSSCs, Onion peel, Lemon leaves, Natural Pigments, Narrowing band-gap

## 40 **Introduction**

41 Every day since the turn of the 20<sup>th</sup> century, there has been an increase in the demand for  
42 energy. Coal, oil, and natural gas are regarded to be the primary energy sources used in today's  
43 society (Zou *et al.* 2016; Dang *et al.* 2018). Fossil fuels are used to create around 90% of all  
44 electricity. Without electricity, society as a whole would fall apart in a day. The majority of the  
45 thermal energy used for industrial and home purposes, in addition to electricity, is produced by  
46 energy sources based on fossil fuels. The issue with producing energy from fossil fuels is that  
47 they are not sustainable and are quickly running out (Sorrell *et al.* 2015; Stuckelberger *et al.*  
48 2017). Additionally, using fossil fuels contributes to environmental problems such ozone layer  
49 loss, acid rain, acid rain, water pollution, air pollution, land pollution and global climate  
50 change. A potential replacement for conventional fossil fuels is the use of sustainable energy  
51 sources, such as solar energy, wind power, hydropower, wave energy, tidal energy, biomass,  
52 and geothermal energy. Unlike traditional fossil fuels, which are concentrated in a small  
53 number of countries, renewable energy resources span a large geographic area (Solangi *et al.*  
54 2011; Zhang *et al.* 2018). The development of low-cost photovoltaic technologies has caught  
55 the interest of both academic and industrial research communities due to the ever-increasing  
56 trend of demand for sustainable energy supply. Solar energy is the easiest to extract from all  
57 other renewable energy sources using a photovoltaic (PV) system. There are three distinct  
58 generations of PV cells: Silicon wafer-based solar cells of the first generation, Copper Indium  
59 Gallium selenide (CIGS), Cadmium Telluride (CdTe) and Gallium Arsenide (GaAs) of the  
60 second generation, and Quantum dot solar cells, Organic solar cells, multi-junction solar cells,  
61 and Dye-sensitized solar cells of the third generation (Khatibi *et al.* 2019; Ole *et al.* 2012).  
62 Third-generation solar cells include the DSSC, often referred to as the Gratzel solar cell. Since  
63 O'Regan and Gratzel first developed a novel type of solar system, DSSC has received a lot of  
64 attention due to its straightforward manufacturing method, environmental friendliness, low cost  
65 of assembly, and good cell performance in low light conditions (O'regan *et al.* 1991). In this  
66 context, dye-sensitized solar cells being researched in particular as effective substitutes for  
67 conventional solar cells due to their desired ecological and economic characteristics, simplicity  
68 in manufacture, and potential for optimising optical qualities through molecular design (Ahmed  
69 *et al.* 2018). The idea of natural photosynthesis served as inspiration for the way DSSCs  
70 function, and pigments are crucial to the devices' ability to respond to a wider range of  
71 wavelengths. Several approaches, including enhanced oxidation processes, dye quantity

72 reduction, and replacement with natural colours, have been put forward by various research  
73 institutions and governmental organisations to address the difficulties of establishing water  
74 treatment technology (Taya *et al.* 2015). The sensitizer, which absorbs sunlight and triggers  
75 the charge separation process, is one of the crucial parts of DSSCs. It is essential to improve  
76 the dyes' capacity for light absorption in order to increase the power conversion efficiency of  
77 DSSCs. Investigation and improvement of the dye-substrate interaction, which plays a role in  
78 the electron transfer process, are also essential. Ruthenium-based dyes, have a high conversion  
79 efficiency of more than 10%, but they are also very expensive and unsustainable (Rajendhiran  
80 *et al.* 2023; Gratzel *et al.* 2009). Natural dye is an alternative to costly, harmful dye that must  
81 has comparable conversion efficiency and is nontoxic, biodegradable, less expensive, and  
82 simple to extract. Natural dyes, which are produced using sustainable bio resources, are  
83 biodegradable, affordable, and ecologically friendly options that can effectively replace  
84 synthetic colours. In DSSCs, natural dyes derived from plants have been proven to be effective  
85 photosensitizers for instance, Abhishek Attri presented a report based on various dyes and  
86 observed a photo conversion efficiency of 0.13% with the use of radish leaves as a sensitizer  
87 (Attri 2019). In present work, we have investigated the performance of DSSC with natural dyes  
88 based on Onion peels and Lemon tree leaves. The study aims to explore the potential of these  
89 natural dyes as photosensitizers for DSSCs. By understanding the electronic properties and  
90 light-harvesting capabilities of the natural dye solution, the improved light absorption and  
91 charge transport within the cell can be optimized. This research aims to identify the potential  
92 of natural pigments with motto to improve the efficiency and sustainability of DSSCs with an  
93 approach to utilise renewable resources to drive clean energy innovation. With the potential to  
94 pave the way for more eco-friendly and accessible solar energy solutions, the natural dyes in  
95 DSSCs represents a step forward in our journey towards a greener and more sustainable future.

## 96 **Experimental Materials**

97 Onion peels, Lemon leaves used in this study as a sensitizer. FTO conductive glass (sheet  
98 resistance:  $7\Omega/\text{sq}$ ), Degussa P25 Titanium dioxide nanopowder (99.5%, Nanoshel India), carbon  
99 nanopowder ( $<100\text{nm}$ , 97%, Sigma Aldrich), Ethyl cellulose, Terpinol, 1-butyle 3-methyl  
100 imidazolium iodide (BMII), lithium iodide (LiI), iodine ( $\text{I}_2$ ), 4-tert butyl pyridine, ethanol,  
101 acetone, 2-propanol, acetonitrile, HCl, 10% Triton X-100 (Fisher Chemical) and valeronitrile etc.  
102 purchased all from Sigma Aldrich.

## 103 **Extraction of Natural Dyes**

104 Onion peels have Anthocyanin and Lemon leaves contain Chlorophyll dyes as natural pigments  
105 (Kumara *et al.* 2013), acidified ethanol was used as the extractant for dye extraction from Onion  
106 peels and while concentrated ethanol was used for Lemon leaves. For this, 06g of Onion peels  
107 were dried and crushed to make a fine powder and mixed in 250 ml of acidified (.01% HCl)  
108 ethanol solution. The mixture was left in the dark room for whole day and after that the dye  
109 extract was filtered with the use of filter paper. For the preparation of lemon leaf dye, 40 g of  
110 air-dried Lemon leaves were crushed into fine powder and disperse into minimum amount of  
111 ethanol (95%) to get concentrated solution. The dispersions were heated for 12 hours at  $60\text{ }^\circ\text{C}$   
112 in closed reflux. Both the dispersions were filtered to get the dye. The subsequent filtering of

113 the solution produced a clean concentrated filtrate that was employed as a natural sensitizer.  
114 All dye preparations were kept in the dark and cool place.

### 115 **Preparation of TiO<sub>2</sub> paste**

116 TiO<sub>2</sub> paste was prepared by mixing 0.5 g titanium oxide (TiO<sub>2</sub>) in 10 mL of ethanol solution.  
117 0.35 g of ethyl cellulose was added to the above mixture, and mixing was done with a magnetic  
118 stirrer after adding few drops of Terpinol (Dhungel *et al.* 2010).

### 119 **Preparation of Photoanode**

120 Firstly, Fluorine-doped tin oxide (FTO) substrates were ultrasonically cleaned in ultrasonicator  
121 bath with deionized water, acetone and 2-propanol for each cycle of 15 min and then treated  
122 by UV-ozone system for 15-20 min. The photoanode were prepared using the method reported  
123 (Lokman *et al.* 2019), with the deposition of three layers of dye coated TiO<sub>2</sub> on top of FTO  
124 substrate by doctor's blade using 3M scotch tape to control the thickness upto 16 micrometres,  
125 annealing is done in a heating furnace for 30 min at 450°C. Subsequently, TiO<sub>2</sub>-coated fluorine-  
126 doped tin oxide (FTO) was stored in a dark area and submerged in the dye solution for a  
127 maximum of 24 hours. The excess dye was removed using ethanol and let to air dry.

### 128 **Preparation of Counter Electrode**

129 The counter electrode was prepared using the same FTO cleaning process and the same blade  
130 method adopted in depositing the TiO<sub>2</sub> making a Carbon nano paste (Kouhnavard *et al.* 2016)  
131 onto the FTO substrate and then film was annealed for 30 minutes at 450°C in a furnace.

### 132 **Fabrication of DSSC**

133 The natural dye-sensitized photoanode and Carbon coated Counter electrode were assembled  
134 together to fabricate a DSSC by adding few drops of redox electrolyte solution (I<sub>3</sub><sup>-</sup>/I<sup>-</sup>) in  
135 between them. The electrolyte solution was prepared deploying 0.1 M LiI, 0.05 M I<sub>2</sub>, 0.6 M BMII,  
136 and 0.5 M 4-tert-butyl pyridine in 17 mL of acetonitrile and 3 mL of Valero nitrile solution. To acquire  
137 a uniform solution, the mixture was stirred for 2 hrs as shown in Fig.2. 1µm thick counter electrode  
138 was prepared by using 10% Triton X-100 as a solvent.


### 139 **Results and Discussion**

140 The absorption spectrum of natural dyes was carried out by UV/Vis/NIR spectrometer  
141 (PerkinElmer lambda 750). Surface morphological study of counter electrode was investigated  
142 by using field emission scanning electron microscope (FESEM- MIRA 3 TESCAN). J-V  
143 performance of DSSC was carried out by solar simulator (Verasol ORIEL LSS-7120) at AM  
144 1.5 G under irradiation. The charge transfer, electronic and ionic processes were investigated  
145 by using Impedance analyser (Auto lab PGSTAT30) at 0V under dark condition.

146

### 147 **UV-VIS NIR Spectroscopy**

148 The specific absorption spectra for the extracts of Lemon and Onion loaded on TiO<sub>2</sub> layer were  
 149 studied. Different DSSCs were prepared using different dyes over the TiO<sub>2</sub> layer. Fig.1 (a,b)  
 150 show the absorption spectra of these samples dissolved in ethanol. The Onion peel extract was  
 151 shown a peak around 370 nm, it's correlated to the anthocyanin. These peaks could enhance  
 152 the charge transfer reaction in the assembled DSSC when placed under solar radiations (Jalali  
 153 *et al.* 2020).

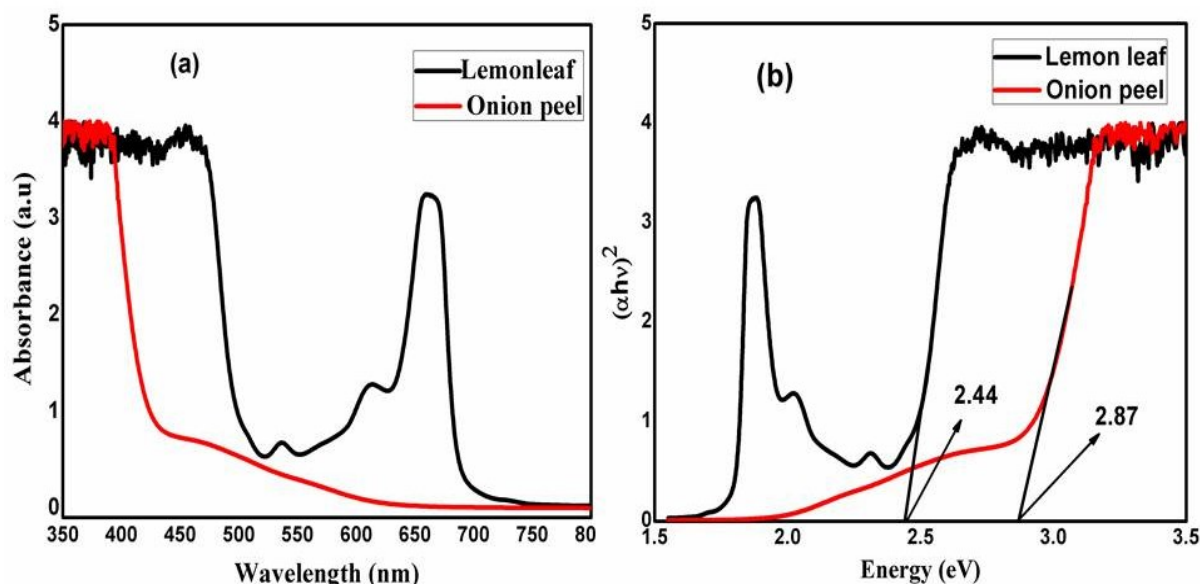

154  
 155 **Figure 1(a) Absorption spectra of TiO<sub>2</sub> coated dyes (b) Tauc plot of different dye coated TiO<sub>2</sub> electrode**

156 Usually, the absorption peaks in visible range are dispersed through the wavelength range of  
 157 400–900 nm. The Lemon leaves extract displayed two major absorption peaks at 475 nm and  
 158 664 nm which represent the component of the dyes extract is chlorophyll (Rekha *et al.* 2019).  
 159 The chlorophyll dye coated TiO<sub>2</sub> represented the first absorption spectral peaks spreading  
 160 between wavelength of 400-490 nm and second absorption wavelength 630-700 nm (Strack *et*  
 161 *al.* 2003; Azeredo *et al.* 2009). The absorbance peak at 400-490 nm indicates the  $\pi \rightarrow \pi^*$   
 162 transition, while the absorptions are observed to peak at 664 nm reflecting the  $n \rightarrow \pi^*$   
 163 transition. Due to conjugated complex structure, transitions in chlorophyll require less energy for any  
 164 electronic transition than in non-conjugated systems (Bruce 2004). In the fabricated DSSC,  
 165 these peaks might be responsible to accelerate the charge transfer reaction under sunlight.  
 166 These results showed that lemon leaf extract coated TiO<sub>2</sub> layer impregnated by chlorophyll  
 167 pigment, which enables it to be employed as DSSC photosensitizers due to their visible  
 168 spectrum light absorption. Lemon leaf dyes have the ability to increase absorbance and expand  
 169 the area where light is absorbed.

170 The energy band gap of the Lemon leaf and Onion peel dyes was calculated using the  
 171 Tauc-plot equation 1 (Khakhal *et al.* 2020)


172 
$$(\alpha h\nu)^2 = \beta(h\nu - E_g) \quad (1)$$

173 Where  $h$ ,  $E_g$ ,  $\beta$ ,  $\alpha$  and  $\nu$  represent Planck constant, band gap, proportionality constant, absorption  
 174 coefficient and frequency respectively. The Tauc's plot for Lemon leaf and Onion peel dyes  
 175 are shown in Fig. 3(b). The bandgap energy of the Lemon leaf and Onion peel dye coated TiO<sub>2</sub>

176 are found 2.44 eV and 2.87 eV respectively, which is lower than the standard band gap of  
177 pristine TiO<sub>2</sub> (3.25eV). As a results, narrowing of the band gap is observed for both dyes,  
178 Lemon leaf band gap energy much more lowered as compare to Onion peel can be ascribed to  
179 more numbers of conjugated bonds due to which the electron may quickly excited from the VB  
180 (valance band) to the CB (conduction band). By providing additional electron states, Natural  
181 dyes can enhance the light absorption properties of TiO<sub>2</sub>, leading to improved photovoltaic  
182 performance (Natrayan et al. 2024).

### 183 Surface Morphology

184 The surface morphology of the TiO<sub>2</sub> nanoparticles coated with Lemon leaf and Onion peel  
185 extracts directly affects the efficiency of DSSCs. The Lemon leaf or Onion peel dye-coated  
186 nanoparticles exhibit a homogeneous particle size distribution. In Fig.2, higher degree of  
187 agglomerated clusters connected to each other on the surface are visible through which electron  
188 transport is established in the resulting DSSCs. Thus, the SEM surface morphology images  
189 reveal that natural pigments are suitable for DSSC as electron acceptors. Optimal surface  
190 characteristics are responsible for improved light absorption, efficient electron transfer, and to  
191 achieve better power conversion efficiency (PCE) in DSSCs (Faisal 2020).

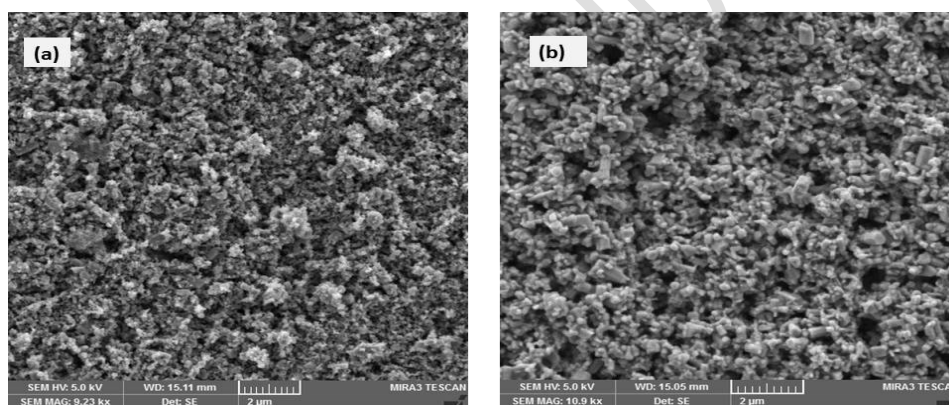


192

193 **Figure 2 FESEM images of (a) Onion peel extract coated TiO<sub>2</sub> (b) Lemon leaf extract coated TiO<sub>2</sub>**

### 194 J-V Characteristics

195 DSSCs were created to test the suitability of natural and direct dye to affordable,  
196 environmentally friendly devices. Fig.3 compares the current density and voltage (J-V  
197 characteristics) of the Lemon leaf dye and Onion peel dye, and Table 1 lists the related  
198 performance metrics with co-operating the current work with some earlier reported results. The  
199 J-V tests were carried out at room temperature with AM 1.5 G illumination (100 mW/cm<sup>2</sup>).  
200 Short circuit current ( $J_{sc}$ ) of 0.49mA/cm<sup>2</sup> and open-circuit voltage ( $V_{oc}$ ) of 0.35 V, FF of 38.02  
201 and efficiency of 0.054 are displayed by DSSCs made using Onion peel dye. In comparison to  
202 Onion peel-based dye, Lemon leaf based DSSC offers high  $J_{sc}$  (0.50mA/cm<sup>2</sup>),  $V_{oc}$  (0.38V),  
203 and FF of 39.46%, all of which contribute to a PCE of (0.92%).

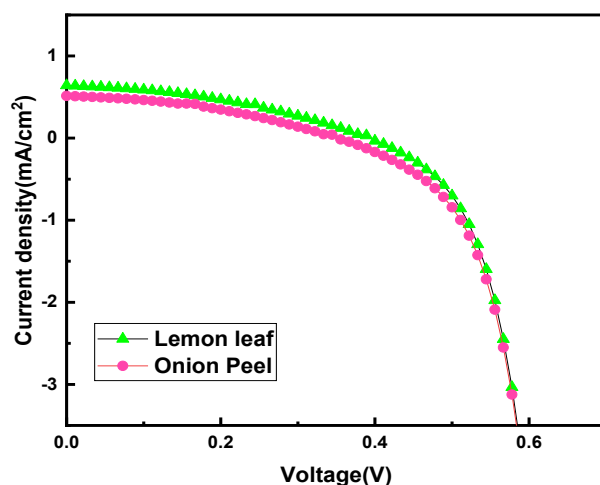

204

205 **Figure 3 Current-voltage curve for DSSC using Lemon leaf and Onion peel dyes at room temperature**  
 206 **under AM 1.5 G illumination condition.**

207 This PCE value of Lemon leaf-based dye is one of the best for DSSC made with natural dyes  
 208 that has been recorded (Kumar et al. 2021; Kharkwal et al. 2021; ADU et al. 2023) .The  
 209 improvement in short circuit current density can be ascribed to increase in dye attachment to  
 210 the surface of TiO<sub>2</sub>. As the TiO<sub>2</sub> surface absorbs more dye molecules it can generate a greater  
 211 number of photons from sunlight, which leads to a rapid electron injection (Inbarajan et al.  
 212 2022). With Lemon leaf electrolyte, the short circuit current density is greater than Onion peel  
 213 electrolyte for DSSC. This is because the electrolytes may have lowered TiO<sub>2</sub>'s Fermi level.  
 214 The DSSC with Lemon leaf electrolyte showed an increase in current density as a result of the  
 215 rate of facile electron injection into the conduction band. Additionally, this may indicate a  
 216 decrease in the rate of electron recombination to the dye's hole and the electrolyte's triiodide  
 217 ion. Nonetheless, there is a 10% difference in the open circuit voltage between the DSSC with  
 218 Lemon leaf electrolyte and the DSSC with Onion peel electrolyte. The Fermi level has been  
 219 decreased in the direction of the redox mediator potential, as this data verifies. This data also  
 220 suggests that iodide ion conductivity has a significant role in the J<sub>sc</sub> of solar cells containing  
 221 I<sup>-</sup>/I<sub>3</sub><sup>-</sup> mediator. Lemon leaf electrolyte has more I<sup>-</sup> ions than Onion peel electrolyte in terms of  
 222 the number density of charge carriers. This demonstrates that the Lemon leaf electrolyte may  
 223 accelerate the exchange of I<sup>-</sup> to I<sub>3</sub><sup>-</sup> and I<sub>3</sub><sup>-</sup> to I<sup>-</sup> ion more quickly, which will cause the dye  
 224 molecules to regenerate fast, while Onion peel electrolyte has shown a lower number of I<sup>-</sup> and  
 225 a slower pace of redox process than Lemon leaf electrolyte (Hassan et al. 2016).

226 **Table 1 Photovoltaic Parameters of DSSCs**


S. No.	Dyes	V <sub>oc</sub> (V)	J <sub>sc</sub> (mA/cm <sup>2</sup> )	FF	Efficiency	Ref.
1.	Onion Peel	0.33	0.96	25.64	0.05	(Adul et al. 2023)
2.	Chlorophyll and Betalain Pigment	0.43	0.09	55.00	0.04	(Philibus et al. 2016)
3.	Onion Peel	0.48	0.24	46.63	0.06	(Ammar et al. 2019)

4.	Red Cabbage	0.51	0.21	46.61	0.06	
5.	Papaya Leaves	0.32	0.36	56.00	0.07	(Suyitno et al. 2015)
6.	Lemon Leaves	0.59	1.08	10.00	0.03	(Maabong et al. 2015)
7.	Onion Peel (A)	0.35	0.49	38.02	<b>0.05</b>	Present Work
8.	Lemon Leaves (B)	0.38	0.50	39.46	<b>0.92</b>	

## 227 Impedance Analysis

228 The impedance spectra, recorded at 0.1 V, spanned a frequency range from 1 Hz to 100 kHz.  
 229 Fig.4 illustrates the Nyquist plot of both dye-based devices in dark conditions. Generally, the  
 230 Nyquist plot of DSSC shows three frequency regions (Kharkwal et al. 2024). The high-  
 231 frequency region can be recognised to the charge transfer resistance at Carbon/electrolyte  
 232 interface. The middle frequency region represents to the charge transfer recombination  
 233 resistance at  $\text{TiO}_2/\text{dye}/\text{electrolyte}$  interface. The low frequency region is represented to the  
 234 diffusion properties of the redox couple ( $\text{I}^-/\text{I}_3^-$ ) in the electrolyte (Ammar et al. 2019). In Table  
 235 3,  $R_s$  and  $R_{\text{rec}}$  represent the series and recombination resistance of the cell. The high value of  
 236 recombination resistances (1704.1  $\Omega$ ) implies a slower rate of electron recombination between  
 237 injected electrons and  $\text{I}_3^-$  in the electrolyte, particularly in Lemon leaf dye (Amogne et al.  
 238 2020). The observed increase in short-circuit current density and conversion efficiency aligns  
 239 with the results of Lemon leaf dye-based device. In Onion peel dye-based devices,  
 240 recombination resistance decreases, as shown in Table 2. The high internal resistance within  
 241 the cell could be the reason of high recombination rate. The DSSC's high internal resistance,  
 242 attributed to significant recombination, leads to poor performance (Ghann et al. 2017). The  
 243 carrier lifetime values precisely correspond to the recombination resistance ( $R_{\text{rec}}$ ) of devices  
 244 with different dyes (Maiaugree et al. 2015).



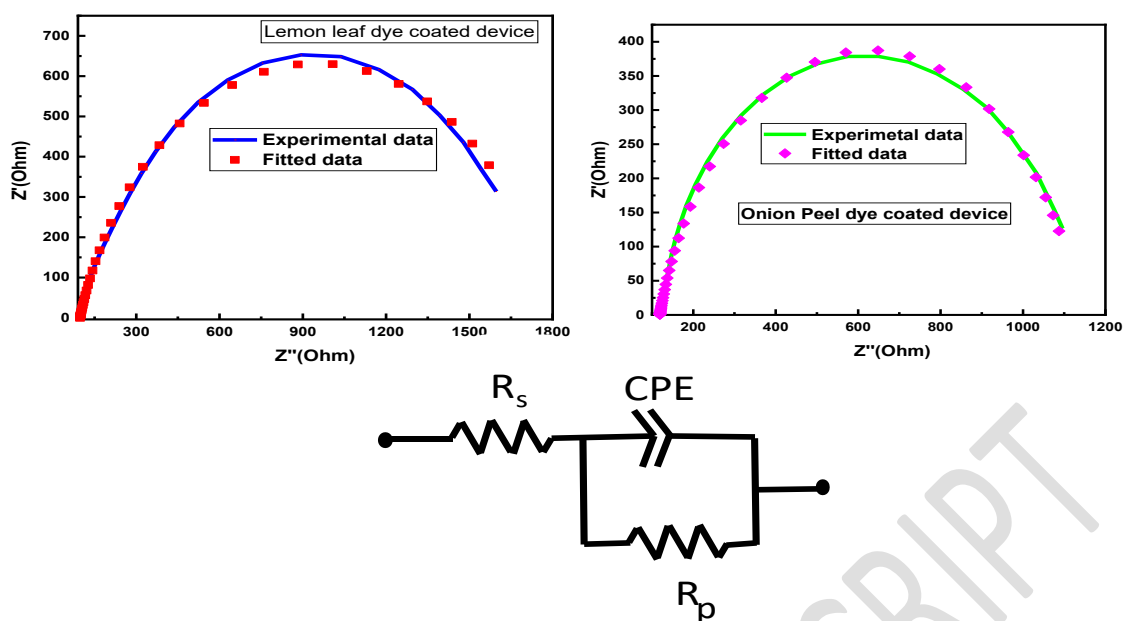

245

246 **Figure 4 Impedance spectra for DSSC made with Lemon leaf and Onion peel dyes. The electrical**  
 247 **equivalent circuit model (EECM) of the DSSCs under study.**

248



249

250 **Figure 5 Schematic of a DSSC sensitized with the extracted dyes**

251 **Table 2 Different Impedance parameters for DSSCs.**

S. No.	Dyes	$R_s(\Omega)$	$R_p(\Omega)$	CPE parameters		Capacitance ( $C_p$ ) ( $\mu F$ )	$\tau_n$ (Sec.)
				$Q_0$	N		
1	Lemon leaf dye	97.51	1704.1	$3.843 \times 10^{-5}$	0.81	$2.045 \times 10^{-5}$	0.0349
2	Onion peel dye	118.74	1020.2	$2.923 \times 10^{-5}$	0.82	$1.403 \times 10^{-5}$	0.0143

252 Lemon leaf-based DSSC exhibits minimal recombination due to efficient charge transfer  
 253 between the dye and  $TiO_2$ . A longer carrier lifetime is associated with higher recombination

254 resistance, and a high diffusion length, restricting from a prolonged carrier lifetime, improves  
255 photocurrent and charge collection rates (Faraz et al. 2021).

## 256 **Conclusion**

257 The outcomes of this research propose that natural dye-based sensitizers can provide fair  
258 photovoltaic performance for DSSCs. The narrowing of band-gap of TiO<sub>2</sub> by the utilization of  
259 Lemon leaf and Onion peel extracts in DSSCs opens up avenues for greener and more  
260 sustainable energy solutions, promoting the development of eco-friendly technologies for a  
261 cleaner and more sustainable future. We optimized factors such as the dye concentration,  
262 annealing temperature, the thickness of the photo-anodes, surface morphology and absorption  
263 of dyes. These parameters were carefully adjusted to maximize the light absorption and charge  
264 transport efficiency of the DSSCs. However, it has been observed that the conversion efficiency  
265 for natural dyes is not sufficient enough for fabricated DSSC, but by considering other factors  
266 like type of electrode materials, electrolytes, mixing of dye solutions etc. may provide better  
267 performance in near future works. It is further observed that in case of Lemon leaf dye-based  
268 device PCE optimized in AM 1.5 G under irradiation is slightly more than Onion peel dye.  
269 Based on our findings, it can be concluded that the natural pigment based DSSCs must be  
270 further investigated as greener, cost-effective, good alternative to the costly Ruthenium  
271 complexes and propose a metal free, climate adaptable solutions in renewable energy sectors.  
272 As the efficiency of DSSC depends on several factors, further investigations on optimization  
273 of some important parameters like materials of electrodes and electrolytes used will be  
274 considered in our future experiments to enhance the efficiency of DSSC using combinational  
275 approach to fabricate DSSC.

## 276 **Acknowledgements**

277  
278 We thank Department of Pure and Applied Chemistry, University of Kota to provide us  
279 necessary laboratory facilities to conduct experimental works. The authors also extend their  
280 appreciation to the Researchers Supporting Project number (RSPD2024R745), King Saud University,  
281 Riyadh, Saudi Arabia.

## 283 **Funding**

284 Researchers Supporting Project number (RSPD2024R745), King Saud University, Riyadh, Saudi  
285 Arabia.

## 286 **References**

- 287 1. Adu R. E. Y., and Gelyaman G. D., (2023) Aqueous Extract of Onion Peels as A  
288 Biowaste-Based Sensitizer for Photovoltaic Cells. *Journal of the Turkish Chemical  
289 Society Section A: Chemistry*, 10(4), 1063-1070.
- 290 2. Adu R. E. Y., Gelyaman G., (2023). Aqueous Extract of Onion Peels as A Biowaste-  
291 Based Sensitizer for Photovoltaic Cells, *JOTCSA*.10(4), 1063-1070.
- 292 3. Ahmed U., Alizadeh M., Abd N., Shahabuddin S., Shakeel M., and Pandey A. K.,  
293 (2018). A comprehensive review on counter electrodes for dye sensitized solar cells : A

- 294 special focus on Pt-TCO free counter electrodes, *Sol. Energy*, 174, no. September, 1097–  
295 1125
- 296 4. Ammar M. A., Hemdan S. H. M., Moataz M. K. Y., Ghada M. A., Ahmed S. H. and  
297 Ahmed S. G. K., (2019). Dye-Sensitized Solar Cells (DSSCs) Based on Extracted  
298 Natural Dyes, *Journal of Nanomaterials*, Article ID 1867271.
- 299 5. Amogne N. Y., Ayele D. W., Tsigie Y. A., (2020). Recent advances in anthocyanin dyes  
300 extracted from plants for dye sensitized solar cell, 9, 23.
- 301 6. Attri A., (2019). Dye-Sensitized Solar Cell Synthesis Using Green Extract: Natural  
302 Approach, *Int. J. Sci. Res.*, 8, 3,71–74.
- 303 7. Azeredo H. M., (2009). Betalains: properties, sources, applications, and stability—a  
304 review. *International journal of food science & technology*, 44(12), 2365-2376.
- 305 8. Bruice P. Y., (2004). Organic Chemistry, Pearson Education, Upper Saddle River, NJ,  
306 USA.
- 307 9. Dang C., Labie R., Simoen E., and Poortmans J., (2018). Detailed structural and  
308 electrical characterization of plated crystalline silicon solar cells, *Solar Energy*  
309 *Materials and Solar Cells*, 184, 57–66.
- 310 10. Danladi E., G. P. Musa, Ezra D. (2016). Chlorophyll and Betalain as Light-Harvesting  
311 Pigments for Nanostructured TiO<sub>2</sub> Based Dye-Sensitized Solar Cells, *Journal of Energy*  
312 *and Natural Reso.*, 5(5),53-58.
- 313 11. Dhungel S. K., Park J. G., (2010). Optimization of paste formulation for TiO<sub>2</sub>  
314 nanoparticles with wide range of size distribution for its application in dye sensitized  
315 solar cells, *Renewable Energy*, 35, 2776-2780.
- 316 12. Faisal S. U., (2020). Performance Investigation of Dye Sensitized Solar Cell using  
317 Hybrid Dyes, *Int. J. Res. Appl. Sci. Eng. Technol.*, 8, 7, 1946–1953.
- 318 13. Faraz S. M., Mazhar M., Shah W., Noor H., Awan Z. H., Sayyad M. H. (2021).  
319 Comparative study of impedance spectroscopy and photovoltaic properties of metallic  
320 and natural dye-based dye sensitized solar cells,  
321 *Physica B: Physics of Condensed Matter*, 602, 412567.
- 322 14. Ghann W., Kang H., Sheikh T., Yadav S., Chavez-Gil T., Nesbitt F. & Uddin J., (2017).  
323 Fabrication, Optimization and Characterization of Natural Dye Sensitized Solar Cell,  
324 *Sci Rep*, 7, 41470.
- 325 15. Grätzel M., (2009). Recent advances in sensitized mesoscopic solar cells. *Accounts of*  
326 *chemical research*, 42(11), 1788-1798.
- 327 16. Hassan H. C., Abidin Z. H. Z., Chowdhury F. I., & Arof A. K. (2016). High efficiency  
328 chlorophyll sensitized solar cell with quasi solid PVA based electrolyte. *International*  
329 *journal of photoenergy*, 3685210
- 330 17. Inbarajan K., Sowmya S., Janarthanan B. (2022). Direct and soxhlet extraction of dyes  
331 from the peels of Allium cepa and its effective application in dye – Sensitized solar cells  
332 as sensitizer, *Optical Materials*, 129, 112487.
- 333 18. Jalali T., Arkian P., Golshan M., Jalali M., & Osfouri S., (2020). Performance evaluation  
334 of natural native dyes as photosensitizer in dye-sensitized solar cells. *Optical*  
335 *Materials*, 110, 110441
- 336 19. Khakhal H. R., Kumar S., Dolia S. N., Dalela B., Vats V. S., Hashmi S. Z., Dalela S.,  
337 (2020). Oxygen vacancies and F<sup>+</sup> centre tailored room temperature ferromagnetic

- 338 properties of CeO<sub>2</sub> nanoparticles with Pr doping concentrations and annealing in  
339 hydrogen environment. *Journal of Alloys and Compounds*, 844, 156079.
- 340 20. Kharkwal, Sharma N., Gupta S. K., and Negi C. M. S., (2021). Enhanced performance  
341 D. of dye-sensitized solar cells by co-sensitization of metal-complex and organic dye,  
342 *Sol. Energy* 230, 1133–1140.
- 343 21. Kharkwal D. and Dhawan A., (2024). Enhanced Performance of Dye-Sensitized Solar  
344 Cells by Mixing of Metal-Complex Dyes, *J. Electron. Mater.* **53**, 5334–5339.
- 345 22. Khatibi A., Astaraei F. R., and Ahmadi M. H., (2019). Generation and combination of  
346 the solar cells: A current model review, *Energy Sci. Eng.*, 7, 2, 305–322.
- 347 23. Kouhnavard M., Ludin N. A., Ghaffari B. V., Sopian K., Karim N. A., Miyake M.  
348 (2016). An Efficient Metal-Free Hydrophilic Carbon as a Counter Electrode for Dye-  
349 Sensitized Solar Cells, *International Journal of Photoenergy*, 5186762
- 350 24. Kumar P. and Kumar V. (2021). Widening spectral range of absorption using natural  
351 dyes : Applications in dye sensitized solar cell, *Mater. Today Proc.*, no. xxxx, 0–3.
- 352 25. Kumara N. T. R. N., Ekanayake P., Lim A., Liew L. Y. C., Iskandar M., Ming L. C.,  
353 and Senadeera G. K. R., (2013). Layered co-sensitization for enhancement of conversion  
354 efficiency of natural dye sensitized solar cells, *Journal of alloys and compounds*, 581,  
355 186-191.
- 356 26. Lokman, Quisar M., Shafie S., Shaban S., Ahmad F., Jaafar H., Rosnan R. M., Yahaya  
357 H., and Abdullah S. S., (2019). Enhancing photocurrent performance based on  
358 photoanode thickness and surface plasmon resonance using Ag-TiO<sub>2</sub> nanocomposites in  
359 dye-sensitized solar cells, *Materials* 12, 13, 2111.
- 360 27. Maabong K., Muiva C. M., Monowe P., Sathiaraj T. S., Hopkins M., Nguyen L.,  
361 Malungwa K., and Thobega M., (2015). Natural Pigments as Photosensitizers for Dye-  
362 sensitized Solar Cells with TiO<sub>2</sub> Thin Film, *INTERNATIONAL JOURNAL OF RENEWABLE*  
363 *ENERGY RESEARCH*, 5, 2, 1-6.
- 364 28. Maiaugree W., Lowpa S., Towannang M., Rutphonsan P., Tangtrakarn A., Pimanpang  
365 S., Maiaugree P., Ratchapolthavisin N., Sang-aroon W., Jarernboon W. &  
366 Amornkitbamrung V., (2015). A dye sensitized solar cell using natural counter electrode  
367 and natural dye derived from mangosteen peel waste, *Scientific Reports*, 5, 15230.
- 368 29. Natrayan L., Surakasi R., Kaliappan S., *et al.* (2024). Effectiveness of natural dye  
369 adsorption on ILSS and optical properties of bio synthesised TiO<sub>2</sub> nano particles and  
370 reinforced with flax seed fiber/epoxy based hybrid composites. *Discov Appl Sci* **6**, 125.
- 371 30. Ole A. F., Santos G. N. C., and Quiroga R. V., (2012). Fabrication and Characterization  
372 of Dye Sensitized Solar Cell Using Nanostructured TiO<sub>2</sub> Photoelectrode, *International*  
373 *Journal of Scientific & Engineering Research*, 3, 8, 1–7.
- 374 31. O'regan B., and Grätzel M., (1991). A low-cost, high-efficiency solar cell based on dye-  
375 sensitized colloidal TiO<sub>2</sub> films. *nature*, 353(6346), 737-740.
- 376 32. Rajendhiran R., *et al.* (2023). Prickly Pear Fruit Extract: Capping Agent for the Sol–Gel  
377 Synthesis of Discrete Titanium Dioxide Nanoparticles and Sensitizer for Dye-Sensitized  
378 Solar Cell, *Coatings*, 13, 3.
- 379 33. Rekha M., Kowsalya M., Ananth S., Vivek P., Jauhar R.M., (2019). Current–voltage  
380 characteristics of new organic natural dye extracted from Terminalia chebula for dye-  
381 sensitized solar cell applications, *J. Optic.* 48 (1) 104–112.

- 382 34. Solangi K. H., Islam M. R., Saidur R., Rahim N. A., and Fayaz H., (2011), A review on  
383 global solar energy policy, *Renew. Sustain. Energy Rev.*, 15, 4, 2149–2163.
- 384 35. Sorrell S., (2015). Reducing energy demand: A review of issues, challenges and  
385 approaches, *Renew. Sustain. Energy Rev.*, 47, 74–82.
- 386 36. Strack D., Vogt T., & Schliemann W., (2003). Recent advances in betalain  
387 research. *Phytochemistry*, 62(3), 247-269.
- 388 37. Stuckelberger M., Biron R., Wyrsh N., Haug F. J., and Ballif C., (2017). Review:  
389 progress in solar cells from hydrogenated amorphous silicon, *Renewable and*  
390 *Sustainable Energy Reviews*, 76, 1497–1523.
- 391 38. Suyitno, Saputra T. J., Supriyanto A., Arifin Z., (2015). Stability and efficiency of dye-  
392 sensitized solar cells based on papaya-leaf dye, *Spectrochimica Acta Part A: Molecular*  
393 *and Biomolecular Spectroscopy*, 148, 99–104.
- 394 39. Taya S. A., El-agez T. M., and Elrefi K. S. (2015). Dye-sensitized solar cells based on  
395 dyes extracted from dried plant leaves, *Turkish Journal of Physics*, 39, 1, 24–30.
- 396 40. Zhang J., Tan H. S., Guo X., Facchetti A., and Yan H., (2018). Material insights and  
397 challenges for non-fullerene organic solar cells based on small molecular acceptors,  
398 *Nature Energy*, 3, 9, 720–731.
- 399 41. Zou C., Zhao Q., Zhang G., and Xiong B., (2016). Energy revolution: From a fossil  
400 energy era to a new energy era, *Nat. Gas Ind. B*, 3, 1, 1–11.